

# The Effects of Fibrin–icariin Nanoparticle Loaded in Poly (lactic-co-glycolic) Acid Scaffold as a Localized Delivery System on Chondrogenesis of Human Adipose-derived Stem Cells

## Abstract

**Background:** Nowadays, cartilage tissue engineering is the best candidate for regeneration of cartilage defects. This study evaluates the effect of fibrin/icariin (ICA) nanoparticles (F/I NPs) on chondrogenesis of stem cells. **Materials and Methods:** F/I NPs were characterized by Dynamic Light Scattering DLS. Poly (lactic-co-glycolic) acid (PLGA)-F/I NP scaffold was fabricated and assessed by scanning electron microscope. Human adipose-derived stem cells (hADSCs) were seeded on scaffold and induced for chondrogenesis. After 14 days, cell viability and gene expression were analyzed by the 3-(4, 5-dimethylthiazol-2-yl)-2, 5-diphenyltetrazolium bromide (MTT) assay. MTT assay and real-time polymerase chain reaction (RT-PCR). **Results:** The size and surface charge of F/I NP were about 28–30 nm and  $-17$ , respectively. The average of pore size of PLGA and PLGA–fibrin/ICA was 230 and 340  $\mu\text{m}$ , respectively. Cell viability of differentiated cells in P/F group was higher than others significantly ( $P \leq 0.05$ ). Furthermore, quantitative RT-PCR analysis demonstrated that ICA upregulated cartilaginous-specific gene expression. Furthermore, the results of the expression of type I collagen revealed that ICA downregulated this gene significantly ( $P < 0.01$ ). **Conclusions:** The results indicated that F/I NP could be a potential factor for chondrogenesis of stem cells and downregulation of fibrocartilage marker.

**Keywords:** Adipose-derived stem cells, chondrogenesis, fibrin nanoparticles, icariin, poly (lactic-co-glycolic) acid

## Introduction

Tissue engineering using stem cells, bioactive molecules, and scaffolds in order to improve biological functions of damaged cartilage is a new therapeutic strategy in regenerative medicine.<sup>[1]</sup> Scaffold structure is considered as the most important factor to create a better interaction between cells, tissue, and bioactive molecules.<sup>[2]</sup> Therefore, the use of specific scaffold with the highest porosity as well as biodegradability will have maximum performance in tissue engineering.

Poly (lactic-co-glycolic) acid (PLGA) is a copolymer with appropriate mechanical properties and biodegradability, which was used for chondrogenic differentiation.<sup>[3,4]</sup> It has been reported that PLGA is a hydrophobic composite and has a low interaction with surrounding cells and tissue.<sup>[5]</sup> As a result, PLGA cannot facilitate cell attachment. Therefore, PLGA often used in combination with other materials has optimal physical

properties and creates a large and accessible surface area for cell anchorage.<sup>[6]</sup>

Fibrin is a hydrogel-forming polymer with natural origin which usually mimics key elements of normal tissue and is able to accumulate extracellular matrix (ECM) components in the space around the cells.<sup>[7]</sup> Previous studies indicated that the hybridization of synthetic and natural derived biodegradable polymers such as fibrin and PLGA is capable to increase cell attachment and proliferation and promote early chondrogenesis<sup>[8]</sup> due to increased cell seeding efficiency and homogeneity. In addition, in a similar experiment, it is reported that fibrin/PLGA hybrid scaffold can be considered as a potential delivery vehicle for cell and growth factors such as transforming growth factor-beta-3 (TGF- $\beta$ 3).<sup>[9]</sup> TGF- $\beta$ 3 as a member of TGF- $\beta$  family is able

Mona Gorji,  
Nazem Ghasemi,  
Mohsen Setayeshmehr<sup>1</sup>,  
Anooshe Zargar<sup>1</sup>,  
Mohammad Kazemi<sup>2</sup>,  
Mitra Soleimani,  
Batool Hashemibeni

From the Department of Anatomical Sciences and Molecular Biology, Faculty of Medicine, Isfahan University of Medical Sciences, <sup>1</sup>Department of Advanced Medical Technology, Biomaterials Nanaotechnology and Tissue Engineering Group, Isfahan University of Medical Sciences, <sup>2</sup>Department of Genetics and Molecular Biology, School of Medicine, Isfahan University of Medical Sciences, Isfahan, Iran

**Address for correspondence:**  
Prof. Batool Hashemibeni,  
Department of Anatomical Sciences and Molecular Biology, Faculty of Medicine, Isfahan University of Medical Sciences, Isfahan, Iran.  
Tel: +98-31-37929153;  
E-mail: hashemibeni@med.mui.ac.ir

This is an open access journal, and articles are distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License, which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.

For reprints contact: [reprints@medknow.com](mailto:reprints@medknow.com)

**How to cite this article:** Gorji M, Ghasemi N, Setayeshmehr M, Zargar A, Kazemi M, Soleimani M, et al. The effects of fibrin–icariin nanoparticle loaded in poly (lactic-co-glycolic) acid scaffold as a localized delivery system on chondrogenesis of human adipose-derived stem cells. *Adv Biomed Res* 2020;9:6.

**Received:** 26 June 2019; **Revised:** 03 August 2019;  
**Accepted:** 05 August 2019; **Published:** 25 February 2020

Access this article online

Website: [www.advbiores.net](http://www.advbiores.net)

DOI: 10.4103/abr.abr\_143\_19

Quick Response Code:



to promote chondrogenesis process through specific receptors and with intracellular signaling.<sup>[10-12]</sup> This factor has a low half-life and high price and have some side effects such as osteophyte formation and synovial membrane inflammation.<sup>[13]</sup> Therefore, to reduce these side effects, the replacement of TGF- $\beta$  with other agents is essential.

Icariin (ICA), an herbal component, widely used in order to treatment of fracture and joint diseases, also can act as a substitute for growth factors in order to promote chondrogenesis of stem cells.<sup>[14]</sup>

The main mechanism of ICA in the treatment of cartilage diseases is not clear. Nevertheless, several potential pathways such as increasing the expressions of cartilage-specific genes,<sup>[15]</sup> decreasing the expression of type I collagen,<sup>[16]</sup> increasing ECM synthesis,<sup>[15]</sup> and anti-inflammatory<sup>[17]</sup> effects may control its pharmacological effects. Since the half-life of the growth factors is short and when delivered exogenously, their efficacy is reduced; nanomaterial based systems as novel therapeutic strategies have become a primary choice for drug delivery due to unique physicochemical properties of nanoparticles.<sup>[18]</sup> Nanoparticles do not have any effect on the biological activity of growth factors and substantially prolong their biological half-life.<sup>[19]</sup> Thus; cell differentiation can be successfully supported by continuous release of growth factors. According to several current published data, nanodrug delivery system by the use of different nanoparticles such as PLGA/hyaluronic acid/fibrin/bioactive glass nanocomposite,<sup>[3]</sup> chitosan nanoparticles,<sup>[20]</sup> and TGF- $\beta$ 1-loaded fibrin–poly (lactide-caprolactone) nanoparticulate<sup>[9,21]</sup> is an attractive system for treatment of cartilage repair.

In this study, we prepared a novel delivery system by combining of PLGA-loaded fibrin–ICA nanoparticle scaffolds as a localized delivery system on chondrogenesis of human adipose-derived mesenchymal stem cells (hADSCs).

## Materials and Methods

### Preparation of fibrin–icariin nanoparticles

Thrombin was prepared by incubation of calcium gluconate (10 ml) and fresh frozen plasma (16 ml) for 90 min. 0.675 mg ICA (Sigma) was added to 5 ml fibrinogen and mixed with thrombin. Fibrin nanoparticles (FNPs) were prepared by dissolving 200 mg of fibrin in 10 ml of NaOH (1 N). To this, diluted HCl (1 N) was added dropwise under vigorous stirring (2000 rpm) which eventually led to the formation of FNPs at pH 5.5; this was milky white color. The FNP was transferred to a dialysis bag for 24 h. Later, FNPs were lyophilized and stored at  $-20^{\circ}\text{C}$ .

### Size and surface charge of fibrin nanoparticles

Surface charge (zeta potential) and size distribution of FNP were determined using Zetasizer Nanoseries (Malvern Instruments, USA).

### Loading of fibrin–icariin nanoparticles in poly (lactic-co-glycolic) acid scaffold

At first, sodium chloride (0.3 g), as a porogen, was poured in each well up to a height of 3 mm. In the next stage, PLGA (22.5 mg) and fibrin–ICA nanoparticles (2.5 mg) were resolved in 1.5 mL of dichloromethane solvent. The prepared solution was vortexed and then was stored. The frozen solution was then transferred into a freeze-drying vessel (Labconco-Freezone, USA) for 48 h to eliminate the solvent.

### Scanning electron microscope imaging

Scanning electron microscope (SEM) (Hitachi S-3400N) was used for the observation of the internal pore morphology of the scaffolds.

### Contact angle measurement

The hydrophilicity and wet ability of the scaffolds were determined using a water contact angle measuring system (WCA Optima, AST Products, Inc. software, model 100-00-220, Ramé-Hart, USA).

### Isolation and culturing of stem cells

hADSCs were isolated and cultured according to our previous studies.<sup>[22]</sup>

### Cell seeding and differentiation

hADSCs ( $10^6$  cells/ml) were suspended in chondrogenic medium and seeded in sterile scaffolds (PLGA/FNP = P/F and PLGA/fibrin–ICA nanoparticles = P/F/I). Each scaffold cell in chondrogenic medium with and without TGF- $\beta$ 3 (10 ng/ml) was incubated for 2 weeks.

### MTT assay

Viability of differentiated cells was assessed by MTT assay according to protocol.<sup>[3]</sup>

### Real-time polymerase chain reaction analysis

Evaluation of SOX9, COLII, COLI, and AGG genes was evaluated by real-time polymerase chain reaction (PCR) technique. Total RNA was isolated by Yekta Tajhiz Azma kit. Complementary DNA (cDNA) was synthesized by the cDNA synthesis kit (YKTA kit). Relative quantification of gene expression was measured using Maxima SYBER® Rox qPCR Master Mix kit (Fermentas). The experiments were performed three times. All primers were designed by the Allele ID software (ver. 7.6) in accordance with Table 1.

### Statistical analysis

The results were analyzed by SPSS Statistics version 21.0 software. One-way ANOVA analysis and least significant

**Table 1: Gene sequences of primers**

Gene	Primer sequences (forward and reverse)
Collagen II-F	CTGGTGATGATGGTGAAG
Collagen II-R	CCTGGATAACCTCTGTGA
Sox-9-F	TTCAGCAGCCAATAAGTG
Sox-9-R	TTCAGCAGCCAATAAGTG
Collagen I-F	CCTCCAGGGCTCCAACGAG
Collagen I-R	TCAATCACTGTCTTGCCCCA
Aggrecan-F	CCTTGGAGGTCGTGGTGAAAGG
Aggrecan-R	AGGTGAACCTCTCTGGCGACGT
GAPDH-F	AAGCTCATTTCTGGTATG
GAPDH-R	CTTCTCTTGTGCTCTTG

difference *post hoc* test were operated with a significance level of  $P < 0.05$ .

## Results

### Size and surface charge of fibrin-icariin nanoparticles

DLS showed that the size of F/I NP almost is 28 nm and zeta potential is  $-17$  mv.

### Scanning electron microscope results

PLGA scaffold exhibited a porous structure and pore size varying from 210 to 250  $\mu\text{m}$  [Figure 1a]. The PLGA/F/ICA scaffold had greater pore size (300–380  $\mu\text{m}$ ) [Figure 1c]. After cell seeding, SEM images of scaffolds indicated the differentiated cells attached and spread within the pore walls with spindle shape and cytoplasmic process in PLGA/F/ICA scaffold and in pure PLGA scaffold cells are spherical without process [Figure 1b and d].

### Contact angle results

The average of contact angle in PLGA, PLGA/F, and PLGA/F/ICA is about  $82^\circ$ ,  $42^\circ$ , and  $27^\circ$ , respectively.

### Human adipose-derived stem cells

Stem cells isolated from human adipose tissue revealed spindle- and stellate-like cells in monolayer culture [Figure 2]. In the third passage, stem cells with fibroblast-like morphology increased.


### MTT assay results

Viability of differentiated cells in P/F, P/F/T, P/F/ICA, and P/F/ICA/T groups was 100%, 62%, 70%, and 60%, respectively. Cell viability in P/F group was higher than others significantly ( $P \leq 0.05$ ) [Figure 3].


### Results of gene expression

The results of real time indicated that cartilage-specific (type II and I collagen and SOX9 and aggrecan) gene expression in the experimental groups is significantly higher than the stem cell group ( $P < 0.01$ ).


Aggrecan gene expression in the PLGA/F, PLGA/F/TGF, PLGA/F/ICA, and PLGA/F/ICA/TGF groups was

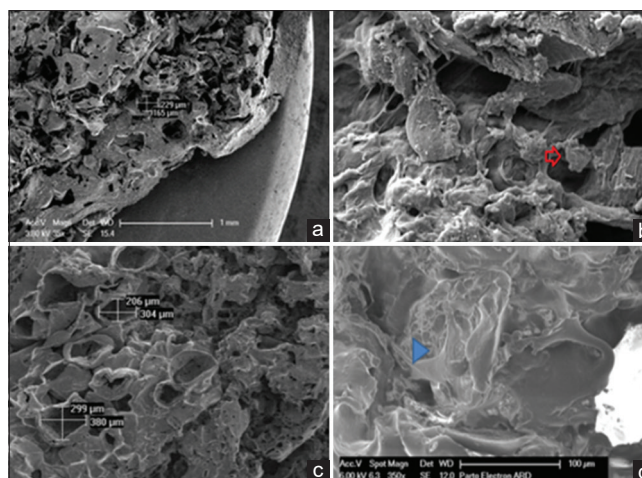

**Figure 1: Scanning electron microscope images of the (a) poly (lactic-co-glycolic) acid, (b) poly (lactic-co-glycolic) acid with adipose-derived stem cells, (c) poly (lactic-co-glycolic) acid/fibrin/icariin, (d) poly (lactic-co-glycolic) acid/fibrin/icariin with adipose-derived stem cells**

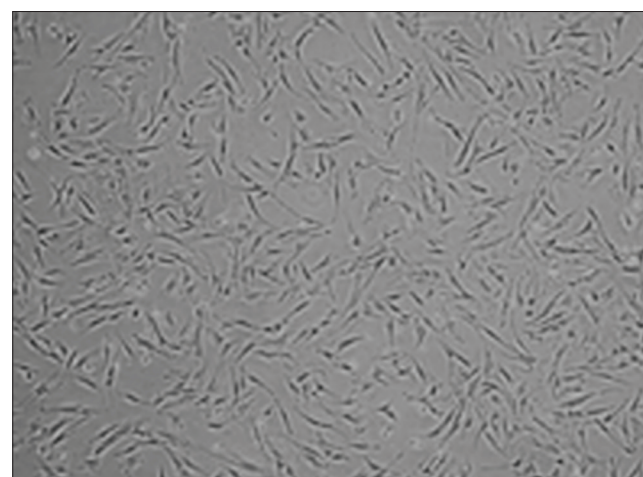

**Figure 2: Human adipose-derived stem cells isolated from adipose tissue in monolayer culture. ( $\times 40$ )**

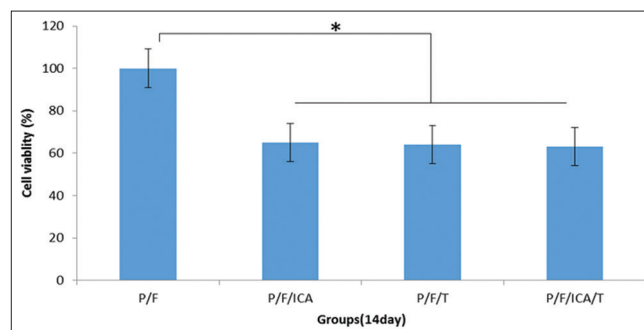

**Figure 3: Comparison of MTT assay results between groups. The viability of cells in poly (lactic-co-glycolic) acid/fibrin scaffold is highest ( $P \leq 0.05$ )**

upregulated 5-, 21-, 19-, and 22-folds compared with undifferentiated stem cells ( $P \leq 0.01$ ). Expression of SOX9, chondrogenic master gene, was increased in PLGA/F: 5 PLGA/F/TGF: 39, PLGA/F/ICA: 63, PLGA/F/ICA/TGF: 85 folds compared with stem cells ( $P \leq 0.01$ ). COLII gene expression was similar in PLGA/F/ICA and PLGA/F/TGF

groups (42 and 49 times, respectively) but in PLGA/F/ICA/TGF group increased 160 folds significantly ( $P \leq 0.01$ ).

The result of real time showed that the mRNA expression of type I collagen (a fibrocartilage marker) was decreased in PLGA/F/ICA group compared with PLGA/F/TGF and PLGA/F/ICA/TGF groups [Figure 4].

### Discussion

The nanoparticles are widely used in drug delivery, regenerative medicine, and tissue engineering researches. The particle size at the nanoscale allows for the study of the effects of biological and drug molecules and the transfer of them to target cells.<sup>[23-26]</sup>

In our study, fibrin-ICA nanoparticles were prepared and loaded in PLGA as a scaffold and localized delivery system for chondrogenic induction of human adipose-derived stem cells into chondrocytes.

DLS measurements revealed that FNPs exhibited particle size in the range of 22–30 nm with the zeta potential value of  $-17.8$  mV in deionized water (pH 6.8) and  $-28$  mV in PBS (pH 7.4). Such negative zeta potential nanoformulations prevent particle aggregation and help repel each particle in the suspension, thus maintaining their stability for a long time.

Some researchers reported different methods for preparation of FNP such as water-in-oil emulsification and cross-linking by the factor XIII or glutaraldehyde.<sup>[27,28]</sup> In our study, no cross-linking agents were used.


Vedakumari *et al.* used wet precipitation method for fabrication of FNPs and reported the FNP size in the range of 25–28 nm with the zeta potential value of  $-10.8$  mV in deionized water (pH 6.8) and  $-23$  mV in PBS (pH 7.4).<sup>[29]</sup> Nanofibrin preparation method and results in our study were similar to Vedakumari report.

PLGA is a Food and Drug Administration-approved material with low immunogenicity, nontoxicity, and biodegradability. However, the lack of cell attachment sites, poor hydrophilicity, and low surface energy are disadvantages of PLGA.<sup>[30,31]</sup>

By impregnating of PLGA with natural polymers such as fibrin for scaffold fabricating, cell adhesion, proliferation, and differentiation could be significantly improved.<sup>[32,33]</sup>

Several previous studies confirmed that the combination of fibrin with PLGA promoted homogeneous cell distribution, cell seeding, and chondrogenesis of stem cells *in vitro* and *in vivo*.<sup>[34,35]</sup>

In our study, the images of SEM indicated that the pore sizes of PLGA/F/ICA scaffold were greater than the PLGA) 340 and 230  $\mu\text{m}$  respectively). NaCl particles with 180–220  $\mu\text{m}$  in size that were employed as a porogen for the fabrication of porous PLGA/F/ICA scaffolds provided enough spaces and proper environment for cell viability and attachment. Unlike the PLGA scaffold, SEM demonstrated a stable three-dimensional and interconnected network microstructure within the PLGA/F/ICA scaffold [Figure 1]. Based on these results, we suppose that the impregnated

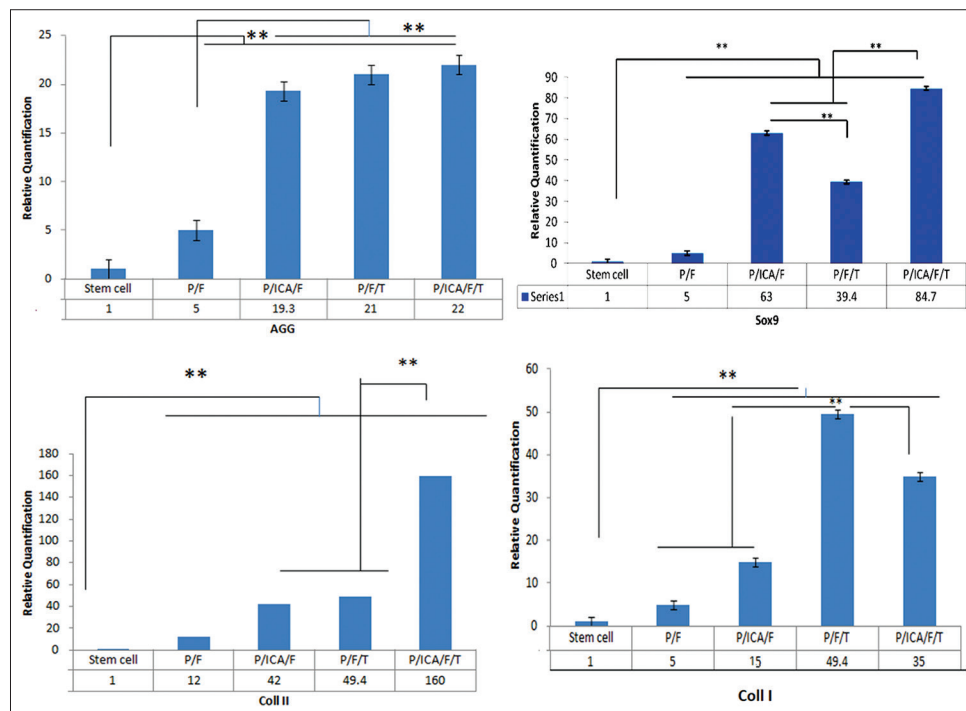

**Figure 4:** The results of real time-polymerase chain reaction indicated AGG, SOX9, type II collagen, and type I collagen genes were expressed in all experimental groups. Gene expression was normalized to housekeeping gene of *GAPDH* and calculated by relative expression compared to stem cells. **\*\***( $P \leq 0.01$ ) P/F (PLGA/FIBRIN), P/ICA/F (PLGA/ICARIIN/FIBRIN), P/F/T (PLGA/FIBRIN/TGF), P/ICA/F/T (PLGA/ICARIIN/FIBRIN/TGF)

F/ICA contributes to the pores and wall surfaces of the PLGA scaffold helping them to support cell attachment and implantation of the engineered constructs for regeneration and repair of injured tissues.

Lien *et al.* showed that pore sizes between 250 and 500  $\mu\text{m}$  of scaffolds are appropriate for chondrocyte proliferation and ECM secretion.<sup>[35]</sup> Cell phenotype, activity, differentiation, and ECM production vary by the size of scaffold pores. When the pore size is about 30 times, the cell diameter differentiated cells are more likely to be chondrocytes.<sup>[36-38]</sup>

Growth factors play a crucial role in the regulation of adult stem cell (ASC) differentiation. A number of studies have demonstrated that bone morphogenetic protein and TGF- $\beta$  are able to induce chondrogenic differentiation *in vitro* and promote the formation of cartilage-like tissue *in vivo*.<sup>[39-42]</sup> Because the low half-time of these growth factors and the high amount of them can result in side effects, delivery system is proposed as a beneficial strategy for release of optimal growth factor or drug.<sup>[43-45]</sup>

Avocado/soybean, ICA, and pomegranate extraction were used in rheumatoid arthritis as an anti-inflammatory drug. ICA is a safe and effective natural anti-inflammatory drug.

Our studies demonstrated that adipose-derived stem cells (ASCs) from human were successfully isolated and were induced to differentiate into chondrocytes on PLGA/fibrin/ICA scaffold with and without TGF- $\beta$ 3.

By comparative observations and evaluations of these constructions in *in vitro* culture, we found that the ICA and TGF- $\beta$  cause in hADSC differentiation into cartilage cells and increase the synthesis of cartilage-specific matrixes. ICA and TGF- $\beta$  together have better chondrogenic effects than one factor alone.

Our results indicated the expression of type II collagen, aggrecan, and SOX9 genes in experimental groups. The presence of ICA in scaffold as a chondrogenic inducer compared with TGF- $\beta$  in medium increased the expression of SOX9 gene. SOX9, a key gene in chondrogenesis and differentiation, promotes the expression of type II collagen and aggrecan.<sup>[46]</sup> Li has demonstrated that the expression of SOX9 significantly increased by ICA as growth factor.<sup>[14]</sup> Similarly, our results indicated that ICA with TGF- $\beta$ 3 enhances the expression of SOX9 considerable.

ICA enhances the expression levels of Smad proteins, including Smad1, Smad4, and Smad5, which are key regulators specific for activation of TGF- $\beta$  signaling pathway and chondrogenic induction.<sup>[47,48]</sup> In addition, ICA upregulates the expression and secretion of various growth factors, including TGF- $\beta$ . Some researchers have proven that ICA is an anabolic agent, which can enhance chondrocyte proliferation and reduce ECM degradation.<sup>[16,47,49]</sup>

Li and *et al.* showed the ICA will upregulate the expressions of cartilage-specific genes of seeded chondrocytes. Furthermore, ICA can increase the synthesis of cartilage matrix, accelerates and maintains the formation of chondroid tissue.<sup>[14]</sup>

Our study also showed that TGF- $\beta$ 3 not only upregulates the expression of hyaline cartilage-specific markers but also unavoidably leads to further hypertrophic differentiation and contributes to the development of fibrous cartilage. The expression of COL I in TGF- $\beta$  and ICA groups was 35.15 times compared with stem cells, respectively. Similarly, other studies found that TGF- $\beta$ 3 alone led to higher expression of type I and X collagens, while ICA downregulated these genes.<sup>[50]</sup>

## Conclusions

The results of this study demonstrated that ICA loaded in PLGA/FNPs could induce chondrogenic differentiation of human adipose-derived stem cells compared with TGF- $\beta$ 3 effectively.

## Financial support and sponsorship

Nil.

## Conflicts of interest

There are no conflicts of interest.

## References

1. O'Brien FJ. Biomaterials and scaffolds for tissue engineering. *Mater Today* 2011;14:88-95.
2. Woo KM, Chen VJ, Ma PX. Nano-fibrous scaffolding architecture selectively enhances protein adsorption contributing to cell attachment. *J Biomed Mater Res A* 2003;67:531-7.
3. Tavakoli E, Mehdikhani-Nahrkhalaji M, Hashemi-Beni B, Zargar-Kharazi A, Kharaziha M. Preparation, characterization and mechanical assessment of poly (lactide-co-glycolide) hyaluronic acid/fibrin/bioactive glass nano-composite scaffolds for cartilage tissue engineering applications. *Procedia Mater Sci* 2015;11:124-30.
4. Mehdikhani-Nahrkhalaji M, Fathi MH, Mortazavi V, Mousavi SB, Hashemi-Beni B, Razavi SM. Novel nanocomposite coating for dental implant applications *in vitro* and *in vivo* evaluation. *J Mater Sci Mater Med* 2012;23:485-95.
5. Kang SW, Seo SW, Choi CY, Kim BS. Porous poly (lactic-co-glycolic acid) microsphere as cell culture substrate and cell transplantation vehicle for adipose tissue engineering. *Tissue Eng Part C Methods* 2008;14:25-34.
6. Song JE, Lee Y, Lee YM, Cho SA, Jang JE, Lee D, *et al.* Effects of PLGA/Fibrin Scaffolds on Attachment and Proliferation of Costal Cartilage Cells. *Polymer Korea*. 2013;37:141-7.
7. Jockenhoevel S, Zund G, Hoerstrup SP, Chalabi K, Sachweh JS, Demircan L, *et al.* Fibrin gel – Advantages of a new scaffold in cardiovascular tissue engineering. *Eur J Cardiothorac Surg* 2001;19:424-30.
8. Munirah S, Kim SH, Ruszymah BH, Khang G. The use of fibrin and poly (lactic-co-glycolic acid) hybrid scaffold for articular cartilage tissue engineering: An *in vivo* analysis. *Eur Cell Mater* 2008;15:41-52.
9. Jung Y, Chung YI, Kim SH, Tae G, Kim YH, Rhie JW,

- et al.* *In situ* chondrogenic differentiation of human adipose tissue-derived stem cells in a TGF-beta loaded fibrin-poly (lactide-caprolactone) nanoparticulate complex. *Biomaterials* 2009;30:4657-64.
10. Longobardi L, O'Rear L, Aakula S, Johnstone B, Shimer K, Chytil A, *et al.* Effect of IGF-I in the chondrogenesis of bone marrow mesenchymal stem cells in the presence or absence of TGF-beta signaling. *J Bone Miner Res* 2006;21:626-36.
  11. Tuli R, Tuli S, Nandi S, Huang X, Manner PA, Hozack WJ, *et al.* Transforming growth factor-beta-mediated chondrogenesis of human mesenchymal progenitor cells involves N-cadherin and mitogen-activated protein kinase and Wnt signaling cross-talk. *J Biol Chem* 2003;278:41227-36.
  12. Nakamura K, Shirai T, Morishita S, Uchida S, Saeki-Miura K, Makishima F. P38 mitogen-activated protein kinase functionally contributes to chondrogenesis induced by growth/differentiation factor-5 in ATDC5 cells. *Exp Cell Res* 1999;250:351-63.
  13. van Beuningen HM, Glansbeek HL, van der Kraan PM, van den Berg WB. Differential effects of local application of BMP-2 or TGF-beta 1 on both articular cartilage composition and osteophyte formation. *Osteoarthritis Cartilage* 1998;6:306-17.
  14. Li D, Yuan T, Zhang X, Xiao Y, Wang R, Fan Y. Icarin: A potential promoting compound for cartilage tissue engineering. *Osteoarthritis Cartilage* 2012;20:1647-56.
  15. Zhang L, Zhang X, Li KF, Li DX, Xiao YM, Fan YJ, *et al.* Icarin promotes extracellular matrix synthesis and gene expression of chondrocytes *in vitro*. *Phytother Res* 2012;26:1385-92.
  16. Sun P, Liu Y, Deng X, Yu C, Dai N, Yuan X, *et al.* An inhibitor of cathepsin K, icariin suppresses cartilage and bone degradation in mice of collagen-induced arthritis. *Phytomedicine* 2013;20:975-9.
  17. Wu J, Du J, Xu C, Le J, Liu B, Xu Y, *et al.* *In vivo* and *in vitro* anti-inflammatory effects of a novel derivative of icariin. *Immunopharmacol Immunotoxicol* 2011;33:49-54.
  18. Jiang W, Kim BY, Rutka JT, Chan WC. Advances and challenges of nanotechnology-based drug delivery systems. *Expert Opin Drug Deliv* 2007;4:621-33.
  19. Tautzenberger A, Kovtun A, Ignatius A. Nanoparticles and their potential for application in bone. *Int J Nanomedicine* 2012;7:4545-57.
  20. Kwon IK, Kidoaki S, Matsuda T. Electrospun nano- to microfiber fabrics made of biodegradable copolyesters: Structural characteristics, mechanical properties and cell adhesion potential. *Biomaterials* 2005;26:3929-39.
  21. Pham QP, Sharma U, Mikos AG. Electrospinning of polymeric nanofibers for tissue engineering applications: A review. *Tissue Eng* 2006;12:1197-211.
  22. Hashemibeni B, Razavi S, Esfandiary E, Karbasi S, Mardani M, Nasresfahani M. Induction of chondrogenic differentiation of human adipose-derived stem cells with TGF-β3 in pellet culture system. *Iran J Basic Med Sci* 2008;11:10-7.
  23. Poirot-Mazères I. Legal aspects of the risks raised by nanotechnologies in the field of medicine. *J Int Bioethique* 2011;22:99-118, 212.
  24. Galvin P, Thompson D, Ryan KB, McCarthy A, Moore AC, Burke CS, *et al.* Nanoparticle-based drug delivery: Case studies for cancer and cardiovascular applications. *Cell Mol Life Sci* 2012;69:389-404.
  25. Sajja HK, East MP, Mao H, Wang YA, Nie S, Yang L. Development of multifunctional nanoparticles for targeted drug delivery and noninvasive imaging of therapeutic effect. *Curr Drug Discov Technol* 2009;6:43-51.
  26. Duncan R. The dawning era of polymer therapeutics. *Nat Rev Drug Discov* 2003;2:347-60.
  27. Praveen G, Sreerekha PR, Menon D, Nair SV, Chennazhi KP. Fibrin nanoconstructs: A novel processing method and their use as controlled delivery agents. *Nanotechnology* 2012;23:095102.
  28. Rajangam T, An SS. Fibrinogen and fibrin based micro and nano scaffolds incorporated with drugs, proteins, cells and genes for therapeutic biomedical applications. *Int J Nanomedicine* 2013;8:3641-62.
  29. Vedakumari WS, Prabu P, Babu SC, Sastry TP. Fibrin nanoparticles as possible vehicles for drug delivery. *Biochim Biophys Acta* 2013;1830:4244-53.
  30. Uematsu K, Hattori K, Ishimoto Y, Yamauchi J, Habata T, Takakura Y, *et al.* Cartilage regeneration using mesenchymal stem cells and a three-dimensional poly-lactic-glycolic acid (PLGA) scaffold. *Biomaterials* 2005;26:4273-9.
  31. Croll TI, O'Connor AJ, Stevens GW, Cooper-White JJ. Controllable surface modification of poly (lactic-co-glycolic acid) (PLGA) by hydrolysis or aminolysis I: Physical, chemical, and theoretical aspects. *Biomacromolecules* 2004;5:463-73.
  32. Sha'ban M, Kim SH, Idrus RB, Khang G. Fibrin and poly (lactic-co-glycolic acid) hybrid scaffold promotes early chondrogenesis of articular chondrocytes: An *in vitro* study. *J Orthop Surg Res* 2008;3:17.
  33. Wu SC, Chang JK, Wang CK, Wang GJ, Ho ML. Enhancement of chondrogenesis of human adipose derived stem cells in a hyaluronan-enriched microenvironment. *Biomaterials* 2010;31:631-40.
  34. Bahrami M, Valiani A, Amirpour N, Ra Rani MZ, Hashemibeni B. Cartilage tissue engineering via icariin and adipose-derived stem cells in fibrin scaffold. *Adv Biomed Res* 2018;7:36.
  35. Lien SM, Ko LY, Huang TJ. Effect of pore size on ECM secretion and cell growth in gelatin scaffold for articular cartilage tissue engineering. *Acta Biomater* 2009;5:670-9.
  36. Grad S, Zhou L, Gogolewski S, Alini M. Chondrocytes seeded onto poly (L/DL-lactide) 80%/20% porous scaffolds: A biochemical evaluation. *J Biomed Mater Res A* 2003;66:571-9.
  37. Lefebvre V, Peeters-Joris C, Vaes G. Production of collagens, collagenase and collagenase inhibitor during the dedifferentiation of articular chondrocytes by serial subcultures. *Biochim Biophys Acta* 1990;1051:266-75.
  38. Widmer MS, Mikos AG. Fabrication of biodegradable polymer scaffolds for tissue engineering. In: *Frontiers in Tissue Engineering*. FTE: Elsevier; 1998. p. 107-20.
  39. Wang W, Li B, Yang J, Xin L, Li Y, Yin H, *et al.* The restoration of full-thickness cartilage defects with BMSCs and TGF-beta 1 loaded PLGA/fibrin gel constructs. *Biomaterials* 2010;31:8964-73.
  40. Kolambkar YM, Peister A, Soker S, Atala A, Guldborg RE. Chondrogenic differentiation of amniotic fluid-derived stem cells. *J Mol Histol* 2007;38:405-13.
  41. Jung MR, Shim IK, Chung HJ, Lee HR, Park YJ, Lee MC, *et al.* Local BMP-7 release from a PLGA scaffolding-matrix for the repair of osteochondral defects in rabbits. *J Control Release* 2012;162:485-91.
  42. Levi B, James AW, Wan DC, Glotzbach JP, Commons GW, Longaker MT. Regulation of human adipose-derived stromal cell osteogenic differentiation by insulin-like growth factor-I and platelet-derived growth factor-alpha. *Plast Reconstr Surg* 2010;126:41-52.
  43. Werle M, Bernkop-Schnürch A. Strategies to improve plasma half life time of peptide and protein drugs. *Amino Acids* 2006;30:351-67.

44. Lee RJ, Springer ML, Blanco-Bose WE, Shaw R, Ursell PC, Blau HM. VEGF gene delivery to myocardium: Deleterious effects of unregulated expression. *Circulation* 2000;102:898-901.
45. Goya G, Grazu V, Ibarra M. Magnetic nanoparticles for cancer therapy. *Curr Nanosci* 2008;4:1-16.
46. Tew SR, Li Y, Pothacharoen P, Tweats LM, Hawkins RE, Hardingham TE. Retroviral transduction with SOX9 enhances re-expression of the chondrocyte phenotype in passaged osteoarthritic human articular chondrocytes. *Osteoarthritis Cartilage* 2005;13:80-9.
47. Hsieh TP, Sheu SY, Sun JS, Chen MH, Liu MH. Icariin isolated from *Epimedium pubescens* regulates osteoblasts anabolism through BMP-2, SMAD4, and cbfa1 expression. *Phytomedicine* 2010;17:414-23.
48. Liang W, Lin M, Li X, Li C, Gao B, Gan H, *et al.* Icariin promotes bone formation via the BMP-2/Smad4 signal transduction pathway in the hFOB 1.19 human osteoblastic cell line. *Int J Mol Med* 2012;30:889-95.
49. Liu MH, Sun JS, Tsai SW, Sheu SY, Chen MH. Icariin protects murine chondrocytes from lipopolysaccharide-induced inflammatory responses and extracellular matrix degradation. *Nutr Res* 2010;30:57-65.
50. Hashemibeni B, Pourentezari M, Valiani A, Zamani M, Mardani M. Effect of icariin on the chondrogenesis of human adipose derived stem cells on poly (lactic-co-glycolic) acid/fibrin composite scaffold. *Int J Adv Biotechnol Res* 2017;8:595-605.